

A Free Energy Model of Boron Carbide

W. P. Huhn & M. Widom

Journal of Statistical Physics

1

ISSN 0022-4715

Volume 150

Number 3

J Stat Phys (2013) 150:432-441

DOI 10.1007/s10955-012-0642-3

Volume 150 • Number 3 • February 2013

Journal of Statistical Physics

Special Issue Dedicated to Michael E. Fisher,
Jerome K. Percus and Benjamin Widom

Available
online
www.springerlink.com

10955 • ISSN 0022-4715
150(3) 413-608 (2013)

 Springer

 Springer

Your article is protected by copyright and all rights are held exclusively by Springer Science +Business Media New York. This e-offprint is for personal use only and shall not be self-archived in electronic repositories. If you wish to self-archive your work, please use the accepted author's version for posting to your own website or your institution's repository. You may further deposit the accepted author's version on a funder's repository at a funder's request, provided it is not made publicly available until 12 months after publication.

A Free Energy Model of Boron Carbide

W.P. Huhn · M. Widom

Received: 9 August 2012 / Accepted: 9 November 2012 / Published online: 4 December 2012
© Springer Science+Business Media New York 2012

Abstract The assessed phase diagram of the boron-carbon system contains a single nonstoichiometric boron-carbide phase of rhombohedral symmetry with a broad, thermodynamically improbable, low temperature composition range. We combine first principles total energy calculations with phenomenological thermodynamic modeling to propose a revised low temperature phase diagram that contains *two* boron-carbide phases of differing symmetries and compositions. One structure has composition B_4C and consists of $B_{11}C$ icosahedra and C-B-C chains, with the placement of carbon on the icosahedron breaking rhombohedral symmetry. This phase is destabilized above 600 K by the configurational entropy of alternate carbon substitutions. The other structure, of ideal composition $B_{13}C_2$, has a broad composition range at high temperature, with rhombohedral symmetry throughout, as observed experimentally.

Keywords Boron carbide · Third law · First principles · Thermodynamics

1 Introduction

The phase diagram of the boron-carbon system is highly controversial and has been frequently revised. In addition to the pure elements, anywhere from one to eight different compound phases are claimed [1, 2], with the sole point of agreement being the existence of a nonstoichiometric boron-rich rhombohedral phase known colloquially as “boron carbide”. Boron carbide is a hard material that is useful in making armor. Owing to the neutron absorbance of boron, it also has uses as a shielding, control and shutdown material in nuclear power plants. In the assessed phase diagram reflecting current consensus, reproduced in Fig. 1, a single phase, labeled as B_4C and exhibiting rhombohedral symmetry, covers a composition range from a low carbon content of 9 % to a high of 19.2 %. Note that the 20 % carbon content implied by the substance name B_4C is never achieved.

W.P. Huhn · M. Widom (✉)
Department of Physics, Carnegie Mellon University, Pittsburgh, PA 15213, USA
e-mail: widom@andrew.cmu.edu

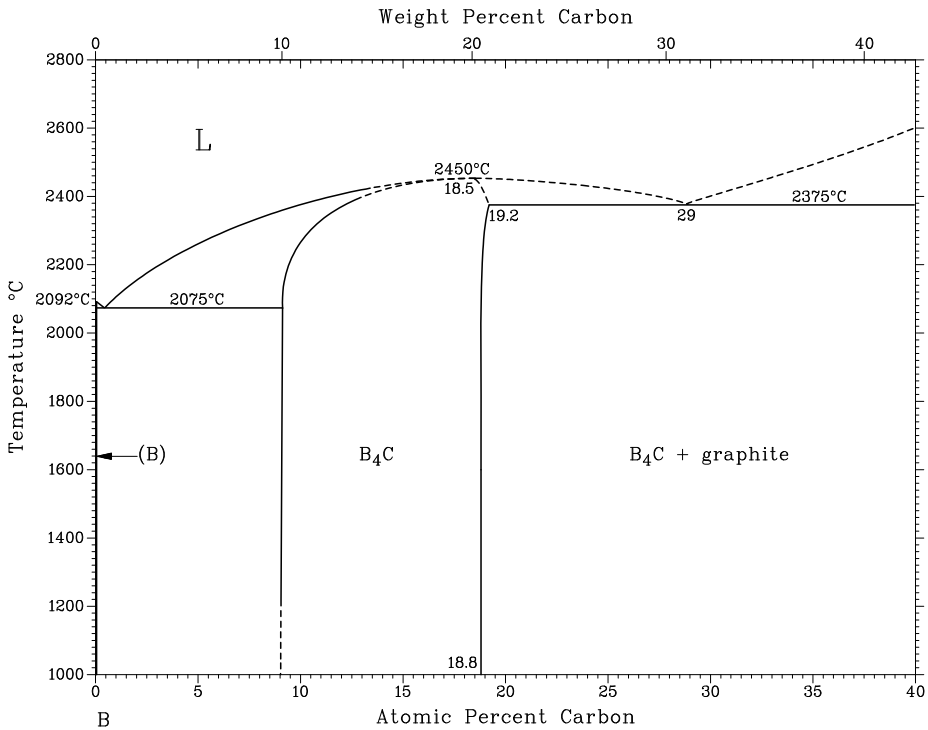


Fig. 1 Assessed phase diagram of the boron carbide system [3]

The broad composition range indicates a substitutional solid solution. The temperature independence of the phase boundaries makes the assessed phase diagram thermodynamically improbable [4]. Specifically, if the phase field were to extend to absolute zero ($T = 0$ K), the positive entropy associated with substitutional disorder would imply a violation of the third law of thermodynamics [5]. Several examples of such apparent violations are known, and generally are resolved by the onset of new phase behavior at low temperatures. One famous example is the dispute over the phase diagram of plutonium-gallium [6], where the American phase diagram extending the composition range of the δ -phase to low temperature was eventually rejected in favor of the Russian version in which δ is stable only at elevated temperature.

Very likely, boron carbide is out of thermodynamic equilibrium at all but the very highest temperatures. In this case, conventional experimentation cannot easily determine the equilibrium phase diagram, and theoretical approaches are needed to resolve the fundamental character of the stable state(s) at low temperature. Previous first principles calculations utilizing electronic density functional theory [7–10] indicate the existence of *two* boron-rich phases, one of ideal stoichiometry $B_{13}C_2$ and rhombohedral symmetry, the other of ideal stoichiometry $B_4C = B_{12}C_3$ and monoclinic symmetry. In the present paper, we introduce a simplified thermodynamic model, inspired by first principles calculations, that elucidates the probable evolution of the equilibrium boron carbide phase field at low temperatures.

Crystallographic refinements [11–13] claim that the B_4C phase has a 15-atom unit cell with rhombohedral symmetry. These papers agree that the boron carbide structure can be viewed in terms of principal structural elements: boron icosahedra linked in a fashion similar

to the α -boron structure, and a linear chain of 3 atoms lying along the 3-fold axis of the unit cell. The atomic positions of the icosahedra belong to two site classes: polar sites linking the icosahedra to each other, and equatorial sites linking the icosahedron to the chains.

The distribution of carbon and boron atoms on these structural elements is uncertain. An idealized $B_{13}C_2$ structure with rhombohedral symmetry occupies the twelve icosahedral sites with boron, while the three-atom chain takes the pattern C-B-C (i.e. the chain center atom is boron and the terminal sites are carbon). However, first principles calculations [7, 14] find that the most stable, enthalpy minimizing, structure is $B_{12}C_3$, with one carbon atom replacing boron on a polar site of the icosahedron, breaking the rhombohedral symmetry. Experimentally [15], the phase appears to contain a mixture of characteristic motifs: B_{12} and $B_{11}C$ icosahedra; C-B-C, B-B-C, B-V-B and C-V-C chains (V = vacancy).

The enthalpy minimizing $B_{12}C_3$ structure has monoclinic symmetry, in disagreement with the B_4C phase's observed rhombohedral symmetry. We propose that the phase known as " B_4C " should be renamed " $B_{13}C_2$ ", or simply "rhombohedral", as we shall do for the remainder of this paper. We also claim that there exists a second phase, which is the true B_4C phase, that we term "monoclinic". In the monoclinic phase, all of the carbons lie on equivalent polar sites of the icosahedra, making a well-ordered structure. Although there is an entropic term corresponding to the choice of this site, it is non-extensive and thus vanishes in the thermodynamic limit. In the absence of substitutional disorder the monoclinic phase is a stoichiometric line compound (i.e., a compound with negligible solubility range at the expected stoichiometry throughout the temperature range of interest, hereafter shortened to "line compound").

In previous work [10], we proposed a phase transition in which the monoclinic phase transitions into the rhombohedral phase through the unlocking of degrees of freedom in the placement of the polar carbons. Because the polar selection breaks the rotational symmetry of the B_{12} icosahedron, we consider this as an orientational degree of freedom. Swapping C atoms among polar sites changes the orientations of the $B_{11}C$ icosahedra. The monoclinic phase aligns all icosahedra identically, while a phase transition to orientational disorder restores rhombohedral symmetry. Landau theory [16] predicts no such transition occurs in the rhombohedral phase, as the symmetry already matches the high T limit. Here, we construct an analytic model to interpret our previous computational results, from which we can derive an actual phase diagram.

2 Free Energy Model

Four solid phases compete for stability: elemental boron (β -rhombohedral), elemental carbon (graphite), and monoclinic and rhombohedral boron carbide. The first three phases are modeled as line compounds throughout the entire temperature range, but rhombohedral boron carbide will be allowed a carbon composition ranging from $B_{14}C_1$ ($x = 1/15 = 0.067$) to $B_{12}C_3$ ($x = 3/15 = 0.200$). The stable $T = 0$ K composition for the rhombohedral phase is $B_{13}C_2$ ($x = 2/15 = 0.133$). According to first principles calculations [10] the most stable $B_{14}C_1$ structure consists of B_{12} icosahedra with B-B-C chains. At composition $B_{12}C_3$ the most stable structure is monoclinic (i.e., not rhombohedral). Rhombohedral structures at this composition correspond to $B_{11}C$ icosahedra with C-B-C chains, but the placement of the carbon atom on the polar sites is randomly oriented among different primitive cells, unlike the monoclinic structure where all polar carbons are uniquely aligned throughout space. Thus our model for the rhombohedral phase allows as structural units B_{12} and $B_{11}C$ icosahedra, and C-B-C and B-B-C chains. Let y_C be the fraction of icosahedra containing a

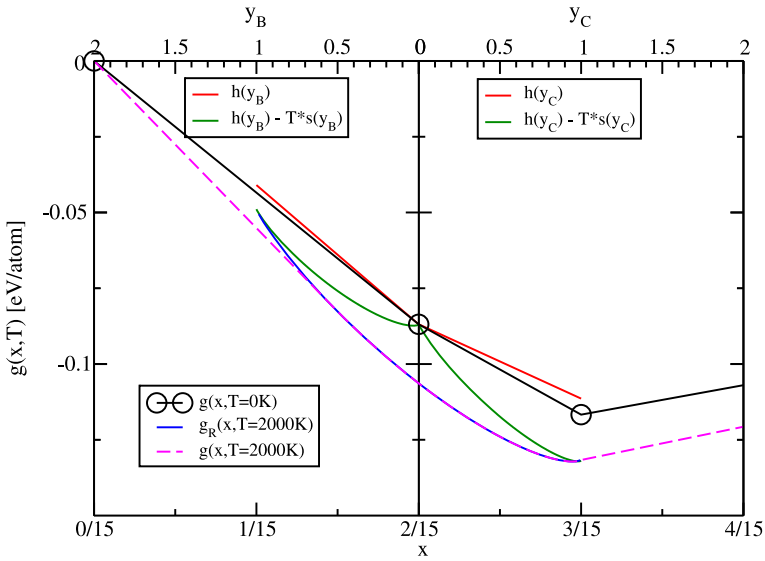


Fig. 2 Components of free energy model. Details in text

polar carbon, and y_B the fraction of chains containing a terminal B. Note that y_B and y_C are bounded between 0 and 1, and that the carbon fraction

$$x = \frac{1}{15}(y_C - y_B + 2). \tag{1}$$

The enthalpies of formation of β -rhombohedral boron and graphite vanish by definition, while we denote the $T = 0$ K enthalpies of the stable rhombohedral and monoclinic boron carbide phases, respectively, as h_R^0 and h_M^0 . Our first principles calculations yielded $h_R^0 = -0.087$ and $h_M^0 = -0.117$ eV/atom (see Fig. 2). Notice that the monoclinic phase is more stable, at $x = 0.200$, than the rhombohedral phase is at $x = 0.133$. We extend the rhombohedral phase entropy beyond its ideal composition by assigning an enthalpic penalty $\beta > 0$ for each excess chain boron and an enthalpic benefit $\gamma < 0$ for each icosahedral polar carbon. Thus $h(y_B) = h_R^0 + \beta y_B$ provided $y_C = 0$ and similarly $h(y_C) = h_R^0 + \gamma y_C$ provided $y_B = 0$, as illustrated in Fig. 2. In general, y_B and y_C are both nonzero, so that

$$h_R(x) = h_R^0 + \beta y_B + \gamma y_C. \tag{2}$$

To complete the free energy model we assign an entropy based on random substitution disorder. Specifically, an ideal site substitutional entropy $-k_B(y \ln y + (1 - y) \ln(1 - y))$ for selecting the fraction y of structural units on which to substitute, together with an intrinsic configurational entropy $k_B \ln 6$ for the orientation of the icosahedral polar carbon, and an intrinsic configurational entropy $k_B \ln 2$ for the choice of terminal chain position, as there are 6 polar sites per icosahedron and 2 terminal sites per chain. Thus,

$$s_R(x) = \frac{k_B}{15}(y_B \ln 2 - y_B \ln y_B - (1 - y_B) \ln(1 - y_B)) + \frac{k_B}{15}(y_C \ln 6 - y_C \ln y_C - (1 - y_C) \ln(1 - y_C)) \tag{3}$$

combines with the enthalpy equation (2) yielding the free energy

$$g_R(x, T) = h_R(x) - T s_R(x). \tag{4}$$

A similar free energy model was proposed by Emin [17], although he supplemented the free energy with an additional bipolaron density that is no longer considered as relevant. As the monoclinic phase is a line compound, no composition dependence is required for its enthalpy, and because the configurational degree of freedom of carbon on the icosahedron is locked, it lacks entropy.

Figure 2 illustrates components of the free energy. Black circles denote the enthalpies h_R^0 and h_M^0 , while the black line segments are the convex hull of free energy $g(x)$ at $T = 0$ K. Red lines and green curves illustrate enthalpy and $T = 2000$ K free energy under the constraint that either y_B or y_C vanishes, taking parameter values $\beta = 0.05$ and $\gamma = -0.024$. The blue curve illustrates the $T = 2000$ K free energy $g_R(x)$ (Eq. (4)) with the constraint relaxed, while the dashed pink line is the full convex hull of free energy $g(x)$.

The free energy $g_R(x)$ in Eq. (4) is to be regarded as a Landau-type free energy, as the order parameters y_B and y_C must still be determined as a function of composition x and temperature T . Note the two order parameters are not independent, as the composition equation (1) implies $(dy_C/dy_B)|_x = 1$. Now, minimizing g_R with respect to y_C yields

$$0 = \left. \frac{dg_{rhomb}}{dy_C} \right|_x = \beta + \gamma + \frac{k_B T}{15} \left(-\ln 12 + \ln \left(\frac{y_B}{1 - y_B} \frac{y_C}{1 - y_C} \right) \right). \tag{5}$$

Substituting for the parameter y_B and rearranging yields a quadratic equation for y_C ,

$$y_C^2(1 - \kappa) + (2 - 15x(1 - \kappa))y_C + \kappa(1 - 15x) = 0 \tag{6}$$

where we define

$$\kappa(T) \equiv 12e^{-15(\beta+\gamma)/k_B T} \tag{7}$$

as a measure of the extent to which polar boron atoms can swap positions with chain terminal carbons, which constitutes the fundamental excitation of the ideal rhombohedral structure.

2.1 $T \rightarrow 0$ K limit

We require that the enthalpy parameters $\beta + \gamma > 0$ to ensure that the ideal rhombohedral structure with $y_B = y_C = 0$ minimize the free energy at $x = 2/15$ in the limit $T = 0$. Hence,

$$\lim_{T \rightarrow 0} \kappa(T) = 0, \tag{8}$$

reducing Eq. (6) to the equation $y_C^2 + (2 - 15x)y_C = 0$ with two solutions: either $y_C = 0$ (and then $y_B = 2 - 15x$), or else $y_C = 15x - 2$ (and then $y_B = 0$). That is, either boron substitutes on chain terminal carbon sites, in which case $y_C = 0$ and $x < 2/15$, or else carbon substitutes on icosahedral polar boron sites in which case $y_B = 0$ and $x > 2/15$. As a function of composition we have

$$y_B = (2 - 15x)\theta(2/15 - x), \quad y_C = (15x - 2)\theta(x - 2/15) \tag{9}$$

where θ is the Heaviside step function.

Although exact only at $T = 0$ K, the essential singularity in κ makes this an excellent approximation over a wide range of temperature, up to 1000 K and sometimes even higher

in the examples discussed later. The approximation represented by Eq. (9) separates the free energy into two branches, an $x < 2/15$ branch where only y_B terms contribute, and an $x > 2/15$ piece where only y_C terms contribute, as illustrated in Fig. 2. In each case, one branch of this piecewise-analytic free energy competes with a line compound, so we next derive a general equation for the phase boundary in this scenario.

2.1.1 Substitutional Disorder Coexisting with a Stoichiometric Line Compound

To find the phase boundaries of rhombohedral boron carbide we must locate the coexistence of our substitutionally disordered phase with the competing phases. Depending on composition and temperature the coexisting phase might be β -rhombohedral boron, monoclinic boron carbide, or graphite. In every case the coexisting phase is treated as a line compound whose free energy is simply its enthalpy. In this section we solve the coexistence equations generally, then apply this solution to specific phase boundaries in the following sections.

Consider the free energy model for substituting on a fraction y of structural units, each with intrinsic multiplicity Ω and enthalpic penalty δ ,

$$g(y, T) = h_R^0 + \delta y - \frac{k_B T}{15} (y \ln \Omega - y \ln y - (1 - y) \ln(1 - y)). \tag{10}$$

Such a free energy represents one of the two branches of our rhombohedral free energy (Eq. (4)) at low temperature. Let this phase coexist with an ordered line compound of free energy $g^* = h^*$ and “composition” y^* . We now wish to find the composition, y' , of the disordered phase that coexists with the ordered phase at y^* .

Coexistence is determined by a double tangent condition, at y' and y^* . Specifically, there exists a straight line $f(y) = f_0 + f_1 y$ that is tangent to g^* at $y = y^*$ and to $g(y, T)$ at $y = y'$. For the line compound, tangency at y^* is the simple condition $f(y^*) = h^*$. For the disordered phase, tangency requires both that $f(y') = g(y', T)$ and that $f' = f_1 = g'(y', T)$, where

$$g'(y, T) = \delta - \frac{k_B T}{15} \left(\ln \Omega - \ln \frac{y}{1 - y} \right). \tag{11}$$

Solving, we find

$$\Omega^{y^*} e^{15(h^* - h_R^0 - \delta y^*)/k_B T} = (y')^{y^*} (1 - y')^{1 - y^*}. \tag{12}$$

In the case where $y' \approx 0$, this equation simplifies to

$$y' \approx \Omega e^{15(h^* - h_R^0 - \delta y^*)/y^* k_B T}, \tag{13}$$

while for $y' \approx 1$, we have

$$y' \approx 1 - \left(\Omega e^{15(h^* - h_R^0 - \delta y^*)/k_B T} \right)^{\frac{1}{1 - y^*}}. \tag{14}$$

2.1.2 Boron-Rich Phase Boundary

We apply this general solution to the specific case of rhombohedral boron carbide coexisting with β -rhombohedral boron. In the notation of the preceding section, $h^* = 0$. There are two cases to consider depending on whether the phase boundary lies to the left or to the right of $x = 2/15$.

Case 1 If the boundary lies at $x \leq 2/15$, so that $y_C = 0$, then we identify $y = y_B$, $\delta = \beta$ and $\Omega = 2$, as the disorder corresponds to substitution of boron onto the terminal chain carbon sites. Also, $y^* = 2$ corresponds to the composition $x = 0$. The requirement that β -rhombohedral boron be stable at $x = 0$ against the boron carbide phase at $y_B = 2$ implies a constraint that $2\beta > -h_R^0$. The phase boundary occurs in the limit of small y , and from Eq. (13) we have

$$y'_B = 2e^{-15(h_R^0+2\beta)/2k_B T}. \tag{15}$$

Case 2 If the boundary lies at $x \geq 2/15$, so that $y_B = 0$, then we identify $y = y_C$, $\delta = \gamma$ and $\Omega = 6$, as the disorder corresponds to substitution of carbon onto the icosahedral polar sites. Also, $y^* = -2$ corresponds to the composition $x = 0$. The requirement that free energy be convex at $x = 2/15$ implies a constraint that $2\gamma > h_R^0$. The phase boundary occurs in the limit of small y , and from Eq. (13) we have

$$y'_C = 6e^{+15(h_R^0-2\gamma)/2k_B T}. \tag{16}$$

To determine if Case 1 or Case 2 occurs, consider the ratio

$$y'_C/y'_B = 3e^{-15(\gamma-\beta-h_R^0)/k_B T}. \tag{17}$$

If $\gamma - \beta - h_R^0$ is positive, then the ratio vanishes at low temperature and the requirement of convexity places us in Case 1. If instead it is negative, then the ratio diverges and we have Case 2.

2.1.3 Carbon Rich Phase Boundaries

Next we apply our general solution to the specific case of rhombohedral boron carbide coexisting with monoclinic boron carbide. Now, in the general notation, $h^* = h_M^0$. As in the case of coexistence with elemental boron, two specific cases are possible. However, the fact that carbon substitution is known to be energetically favorable (i.e. $\gamma < 0$) implies that only the case of $y_B = 0$ and $y = y_C$ is relevant. Thus we identify $\delta = \gamma$ and $\Omega = 6$. Noting that the condition for low temperature stability of monoclinic B_4C against disordered rhombohedral at $x = 3/15$ is $h_R^0 + \gamma > h_M^0$, the phase boundary occurs in the limit of small y' , and from Eq. (13) we have

$$y'_C = 6e^{-15(h_R^0-h_M^0+\gamma)/k_B T} \tag{18}$$

as the phase boundary in coexistence with the monoclinic phase.

However, above a certain temperature T_0 the rhombohedral phase coexists with graphite. We assume T_0 lies in the low temperature limit, and find the general form for the phase boundary due to coexistence between graphite and the rhombohedral phase. In our general notation, $y^* = 13$, $y = y_C$, $\delta = \gamma$ and $\Omega = 6$. In contrast to the preceding cases, the phase boundary occurs in the limit of $y \approx 1$, and from Eq. (14) we have

$$y'_C = 1 - 6^{-\frac{13}{12}} e^{15(h_R^0+13\beta)12k_B T} \tag{19}$$

as the phase boundary in coexistence with graphite. The two carbon-rich boundaries cross at a certain temperature T_0 that can be determined by setting the values of y'_C equal in Eqs. (18) and (19). For realistic parameters, the crossing occurs at $y_C \approx 1$. Then from Eq. (18) we find

$$T_0 \approx 15(h_R^0 - h_M^0 + \gamma)/k_B \ln 6. \tag{20}$$

Table 1 Parameters for the rhombohedral phase obtained from first principles calculations

Parameter	Value (eV/atom)
h_R^0	-0.0869
h_M^0	-0.1167
β	0.1031
γ	-0.0244

2.2 Analytic $T = \infty$ Limit

We now examine the high temperature limit for the free energy model. For all possible values of β and γ we have $\lim_{T \rightarrow \infty} \kappa(T) = 12$ giving the quadratic equation $-11y_C^2 + (2 + 165x)y_C + 12(1 - 15x) = 0$, only one of whose roots is physical: $y_C = \frac{1}{22}(2 + 165x - \sqrt{532 - 7260x + 27225x^2})$. Notice that only the multiplicities enter into this equation. Although this equation is more complicated than the one obtained for the low temperature limit, it is defined across the composition range from $x = 1/15$ to $x = 3/15$. The phase boundary on the boron rich side, x'_{boron} , is given by

$$\left. \frac{dg_R}{dx} \right|_{x=x'_{\text{boron}}} = \frac{h_{\beta\text{-boron}} - g_R(x'_{\text{boron}}, T)}{0 - x'_{\text{boron}}} \tag{21}$$

and the phase boundary on the carbon rich side x'_{carbon} is given by

$$\left. \frac{dg_R}{dx} \right|_{x=x'_{\text{carbon}}} = \frac{h_{\text{graphite}} - g_R(x'_{\text{carbon}}, T)}{1 - x'_{\text{carbon}}} \tag{22}$$

The high temperature limits are dominated by the entropic terms, yielding nonlinear implicit equations for x' . Using a numeric equation solver we find $x'_{\text{boron}} = 0.1095$ and $x'_{\text{carbon}} = 0.1515$. However these values are reached only at extreme high temperatures, while our model is intended only for use below the melting temperature.

3 Realistic Parameter Values

Our simple model depends on just four parameters, h_R^0, h_M^0, β and γ . Of these, the values of $h_{R,M}^0$ are easily determined from first principles calculations with simple idealized models. Estimated values of β and γ may be obtained by inserting a single B or C substitutional defect into a hexagonal supercell of the ideal rhombohedral $B_{13}C_2$ structure. Results for a $2 \times 2 \times 2$ supercell were similar. A general description of the computational method is in Ref. [10]. Resulting values are listed in Table 1. These parameters obey the constraints discussed in previous sections. Because $\gamma - \beta - h_R^0 = -0.0406$ is negative, we are in Case 2 as discussed in Sect. 2.1.2 where $x'_{\text{boron}} > 2/15$ at low temperature, although it eventually goes to $x'_{\text{boron}} < 2/15$ at very high temperatures.

There is some question whether our structural model is complete in the B-rich limit, as alternate structure models contain additional interstitial sites in the chain region, some only partially occupied [13, 18, 19]. To take into account a possible influence of these additional sites, we investigate the effect of reducing the value of β , in order to model the effect of lower boron-rich enthalpies. Note that increased multiplicity Ω would also enter the free energy linearly in y_B , though with an added factor of temperature T .

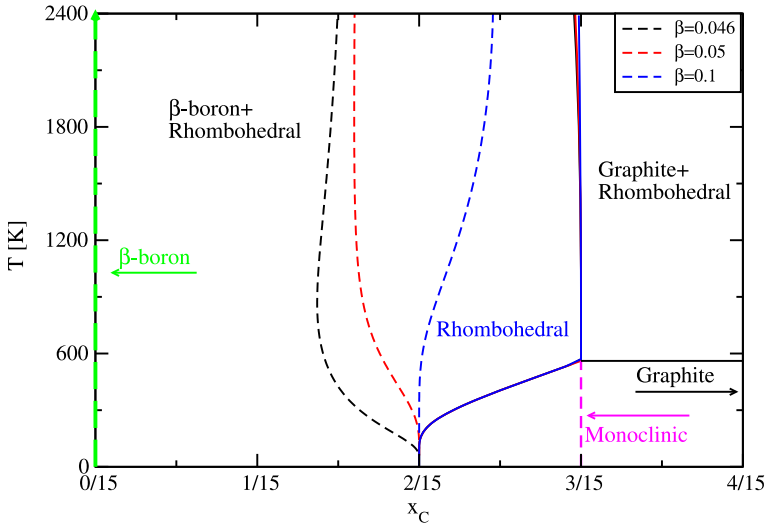


Fig. 3 Predicted phase boundaries for our model using calculated parameters as listed in Table 1 and a selection of values of β . Line compounds are β -boron at $x = 0$, graphite (not shown) at $x = 1$ and monoclinic boron carbide at $x = 3/15$. Carbon-rich phase boundaries of rhombohedral boron carbide are shown as *solid lines*, while boron-rich phase boundaries are shown as *dashed lines*

Results for a selection of values of β are shown in Fig. 3. As expected, the monoclinic phase is destabilized above a temperature $T_0 \approx 600$ K, at which it decomposes into a coexistence of carbon-rich rhombohedral phase together with graphite. This value of T_0 is surprisingly consistent with the location of the heat capacity peak previously reported that was obtained from a completely different method [10]. The maximum carbon content of the rhombohedral phase is bounded below 20 %, owing to the logarithmic singularity in $s(y)$ at $y_c = 1$ creating an infinite slope in $g(x, T)$ (too weak to be visible in Fig. 2). Note that the Gibbs phase rule [4] implies that rhombohedral and monoclinic boron carbide must have differing compositions while in coexistence with graphite, hence $x'_C = 0.2000$ is forbidden in principle.

At temperature 2400 K (around the melting point) the maximum carbon content depends on the value of β , and ranges from 19.9 % down to 19.7 % in our model for the given range of β considered, whereas the experimentally assessed limit is 19.2 %. The phase boundary in coexistence with boron depends strongly on the value of β , as can be seen in Fig. 3. The experimentally assessed limit is 9 % carbon, but over the range of β values studied here, the limit ranges from 10–16 % carbon, strictly above the assessed value. This is a further indication of inadequacy of our model in the boron-rich limit.

4 Conclusion

In this paper we propose a simple free energy model for boron carbide. We predict the existence of two low temperature compounds, resolving the mystery of the assessed low temperature composition range. One phase, whose ideal composition is $B_{13}C_2$, has rhombohedral symmetry throughout its wide high temperature composition range, consistent with experimental observations. The other phase is a line compound of exact stoichiometry B_4C

characterized by an array of parallel $B_{11}C$ icosahedra whose symmetry is monoclinic. Despite its favorable low enthalpy, this monoclinic phase is predicted to be stable only below $T = 600$ K, a temperature so low that it might not be possible to form in thermodynamic equilibrium. This is likely the reason it has never been observed experimentally. Various limiting behaviors of the model phase boundaries are derived analytically, including the key fact that $x'_{\text{carbon}} < 0.200$ in the rhombohedral phase. A quantitative discrepancy in the boron-rich limit reveals the need for further enhancement of our model. Effects to consider include the additional interstitial sites in the chain region and vacancies, as well as electronic and vibrational [20] entropy and thermal expansion.

References

1. Domnich, V., Reynaud, S., Haber, R.A., Chhowalla, M.: *J. Am. Ceram. Soc.* **94**, 3605 (2011)
2. Springer materials (2012). <http://www.springermaterials.com>
3. Okamoto, H.: *J. Phase Equilib.* **13**, 436 (1992)
4. Okamoto, H., Massalski, T.B.: *J. Phase Equilib.* **12**, 148 (1991)
5. Abriata, J.P., Laughlin, D.E.: *Prog. Mater. Sci.* **49**, 367 (2004)
6. Hecker, S.: *Los Alamos Sci.* **26**, 244 (2000)
7. Mauri, F., Vast, N., Pickard, C.J.: *Phys. Rev. Lett.* **87**, 085506 (2001)
8. Saal, J., Shang, S., Liu, Z.K.: *Appl. Phys. Lett.* **91**, 231915 (2007)
9. Vast, N., Sjakaste, J., Betranhandy, E.: *Inst. Phys. Conf. Ser.* **176**, 012002 (2009)
10. Widom, M., Huhn, W.P.: *Solid State Sci.* (2012). <http://dx.doi.org/10.1016/j.solidstatesciences.2012.05.010>. <http://arxiv.org/abs/1111.1737>
11. Clark, H.K., Hoard, J.L.: *J. Am. Chem. Soc.* **65**, 2115–2119 (1943)
12. Will, G., Kossobutzki, K.H.: *J. Less-Common Met.* **44**, 87 (1976)
13. Kwei, G.H., Morosin, B.: *J. Phys. Chem.* **100**, 8031 (1996)
14. Bylander, D.M., Kleinman, L.: *Phys. Rev. B* **42**, 1394 (1990)
15. Schmechel, R., Werheit, H.: *J. Solid State Chem.* **154**, 61 (2000)
16. Landau, L.D.: *On the Theory of Phase Transitions. The Collected Papers of L.D. Landau.* Pergamon, Elmsford (1965)
17. Emin, D.: *Phys. Rev. B* **38**, 6041 (1988)
18. Yakel, H.L.: *Acta Crystallogr.* **31**, 1797 (1975)
19. Morosin, B., Kwei, G.H., Lawson, A.C., Aselage, T.L., Emin, D.: *J. Alloys Compd.* **226**, 121 (1995)
20. Shirai, K., Emura, S.: *J. Solid State Chem.* **154**, 20 (2000)